

## 試驗報告



報告編號：KK-16-07147Z

頁數：1 OF 9

報告日期：106 年 01 月 25 日

委託單位：唐榮鐵工廠股份有限公司

地址：高雄市小港區沿海二路四號

產品名稱：不銹鋼

產品型號：304

產品顏色：銀色

製造廠商：唐榮鐵工廠股份有限公司

收件日期：105 年 07 月 27 日

試驗日期：105 年 07 月 27 日~105 年 12 月 08 日

試驗方法：ASTM B117-11

備註：1.以上資料由顧客提供(收件及試驗日期除外)

2.除非另有說明，此報告結果僅對測試之樣品負責

未經本公司事先書面同意，此報告不可部分複製

## 試驗結果：

## 鹽霧試驗：

試件名稱	鋼捲號碼	試驗前	試驗後
304 不銹鋼-1	Q3922	如附照片 2 OF 9	試驗 1920 小時觀察，測試結果無腐蝕，如附照片 3 OF 9 試驗 2160 小時觀察，測試結果產生點狀腐蝕，如附照片 4 OF 9 試驗 2200 小時觀察，測試結果產生點狀腐蝕，如附照片 5 OF 9
304 不銹鋼-2	Q3922	如附照片 6 OF 9	試驗 1920 小時觀察，測試結果無腐蝕，如附照片 7 OF 9 試驗 2160 小時觀察，測試結果無腐蝕，如附照片 8 OF 9 試驗 2200 小時觀察，測試結果無腐蝕，如附照片 9 OF 9

## 測試條件：

1.鹽液濃度	: 4~6 %	6.測試時間	: 2200 Hour
2.收集鹽霧酸鹼值	: 6.9~7.0	7.噴霧量	: 1.0~1.1 ml/hr
3.供給空氣壓力	: 1.0 kgf/cm <sup>2</sup>	8.收集鹽霧比重	: 1.032~1.033
4.鹽霧室之溫度	: 35.0±2.0℃	9.試件與垂直線角度	: 23°
5.飽和空氣溫度	: 46.0~49.0℃	10.試件尺寸	: 70mm×154 mm

----- 1 -----

本報告若有提供規範值，該規範值僅供參考，合格之判定以委託單位實際要求為準

林忠政  
報告簽署人

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

## 試驗報告

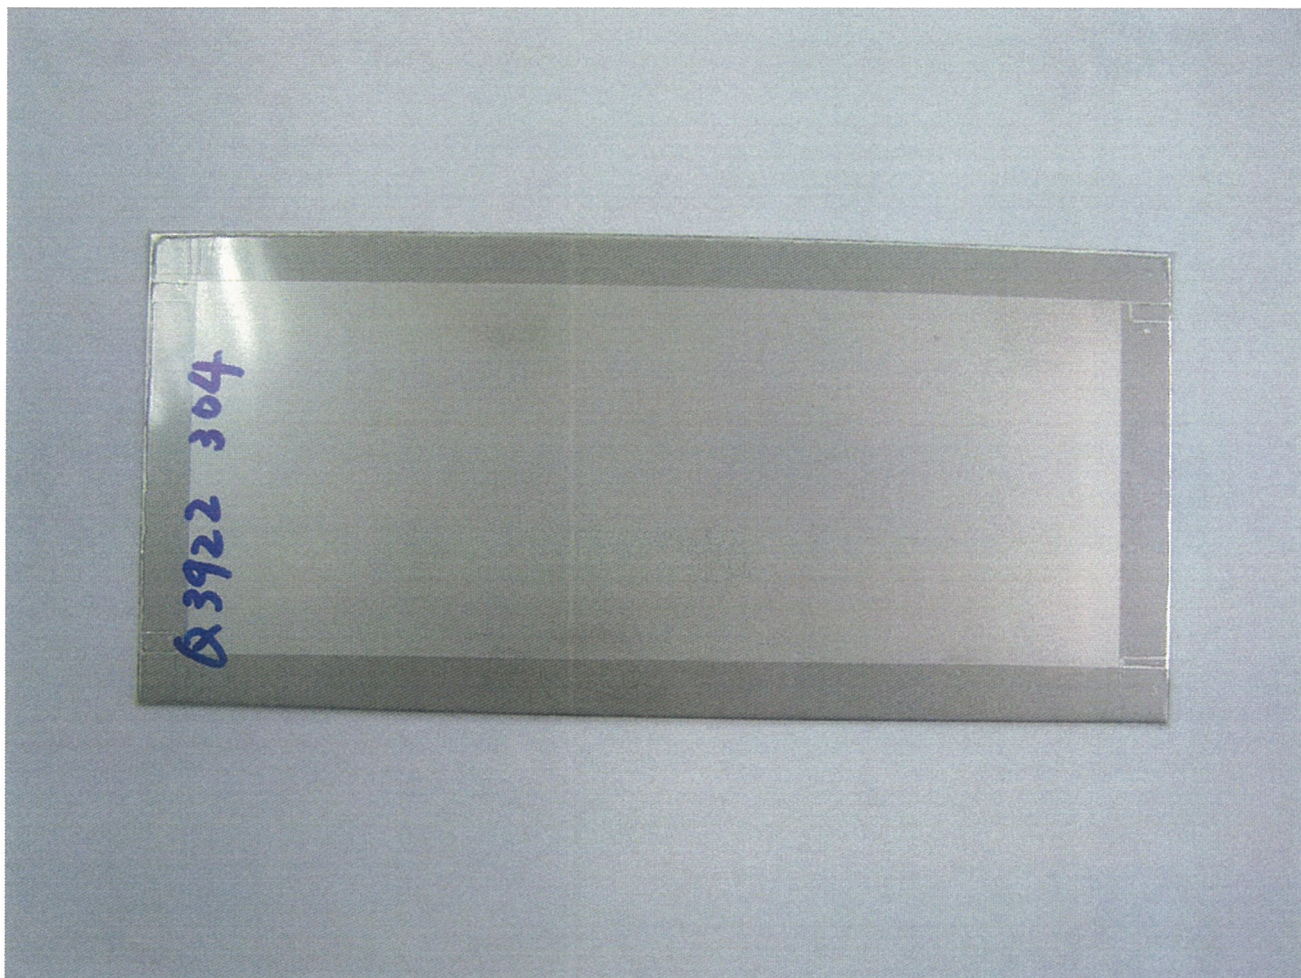


報告編號：KK-16-07147Z

頁數：2 OF 9

報告日期：106 年 01 月 25 日

=====  
試驗結果：



試件名稱：304 不銹鋼-1

試驗前

----- 2 -----

本報告若有提供規範值，該規範值僅供參考，合格之判定以委託單位實際要求為準

  
報告簽署人

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

TWC0576649



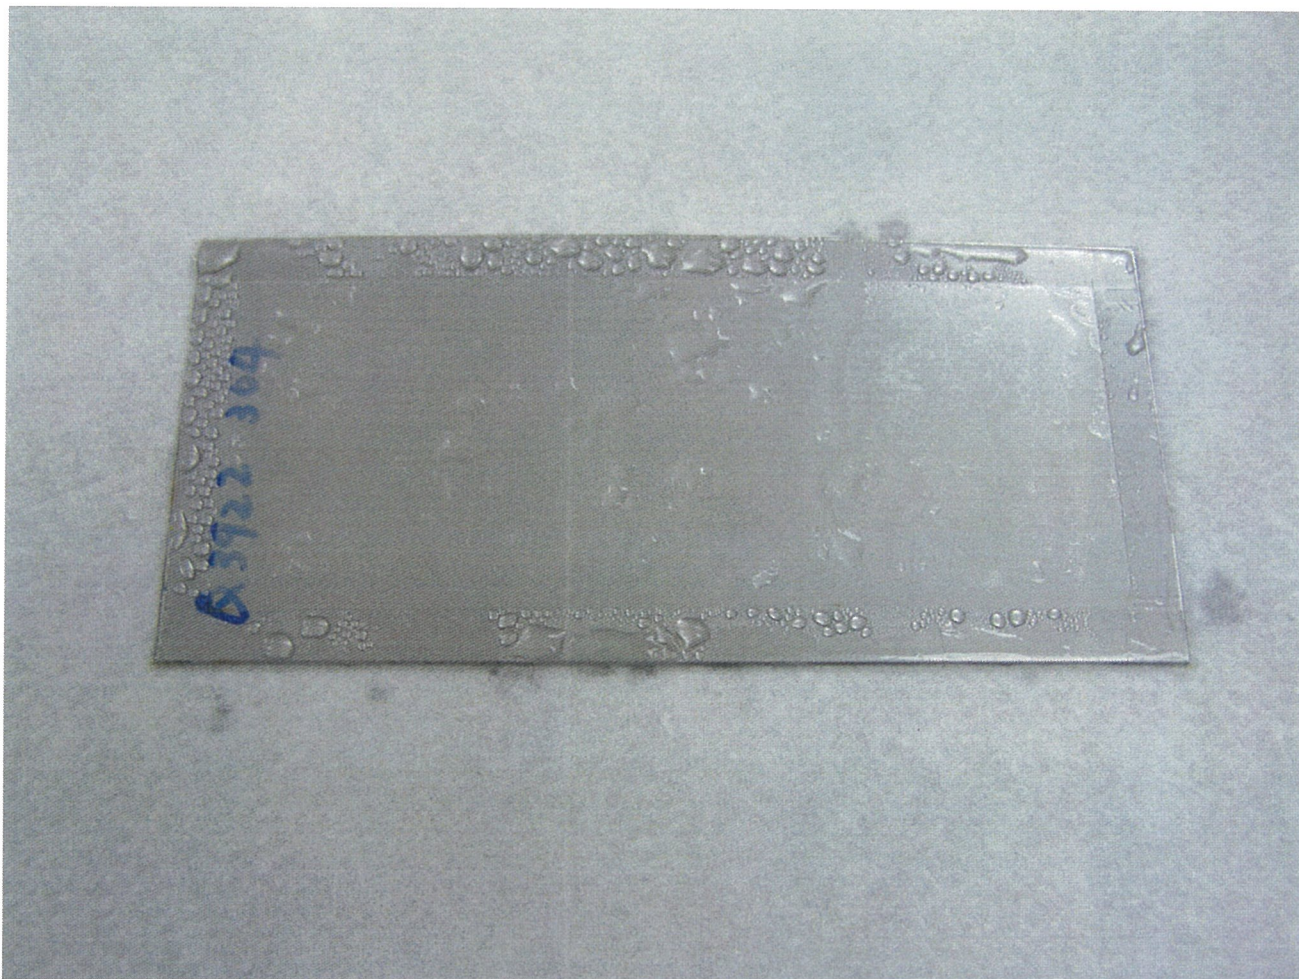
## 試驗報告



報告編號: KK-16-07147Z

頁數: 3 OF 9

報告日期: 106 年 01 月 25 日

=====  
試驗結果:

試件名稱: 304 不銹鋼-1

試驗 1920 小時後

----- 3 -----

本報告若有提供規範值, 該規範值僅供參考, 合格之判定以委託單位實際要求為準

  
報告簽署人

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.



# 試驗報告

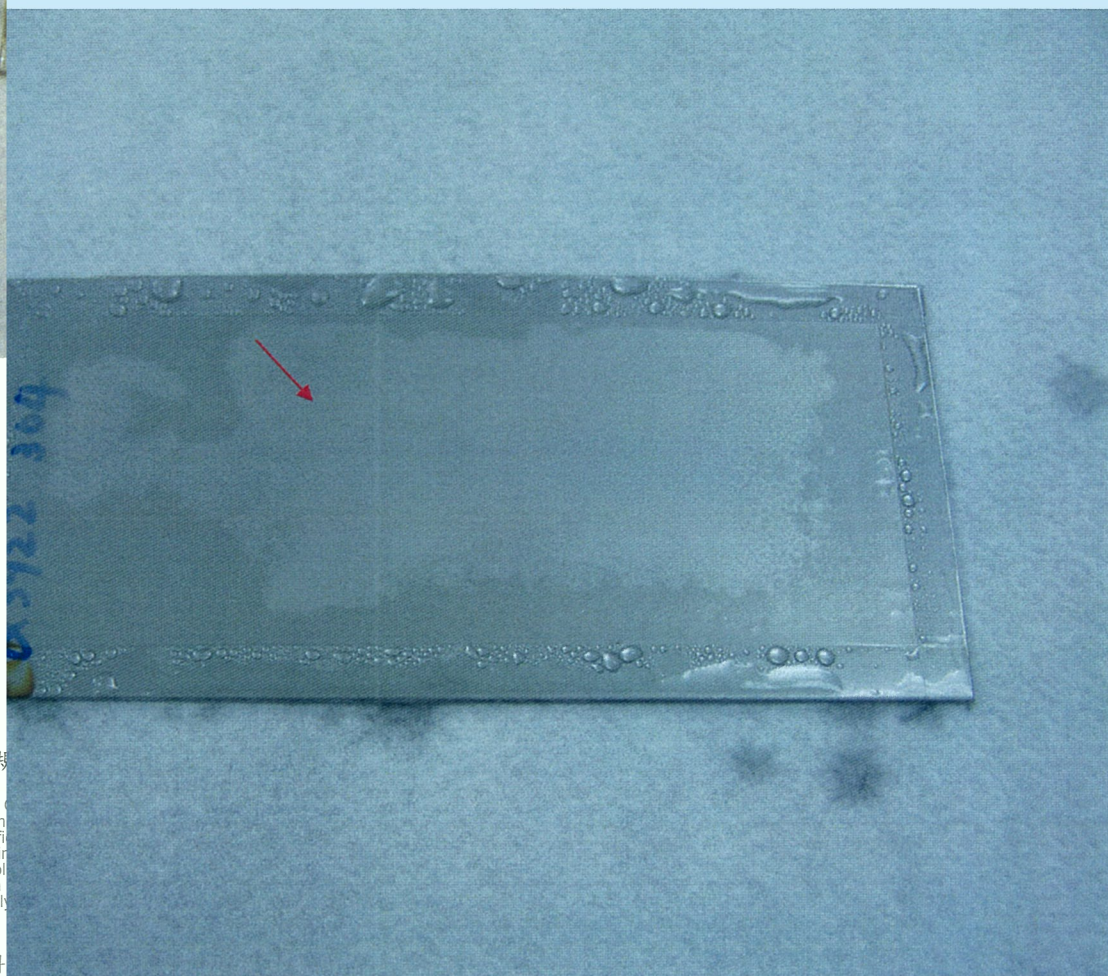


報告編號：KK-16-07147Z

頁數：4 OF 9

報告日期：106 年 01 月 25 日

試驗結果：



試件名稱：304 不銹鋼-1

試驗 2160 小時後

----- 4 -----

杯尚双  
報告簽署人

該規範值僅供參考，合格之判定以委託單位實際要求為準

本報告若有提供規範值

This document is issued by the Company and, for electronic format documents, is subject to the limitation of liability, indemnification, of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from alteration, forgery or falsification of the shown in this test report refer only to the

Sample(s) tested.

SGS  
有限公司

No.61, Kai -Fa Road, Nanzih Export Processing Zone, Kaohsiung, Taiwan / 高雄市楠梓加工出口區開發路61號

t (886-7) 301-2121

f (886-7) 301-1165

www.sgs.tw

Member of SGS Group

TWC0576651

niwei\_lee



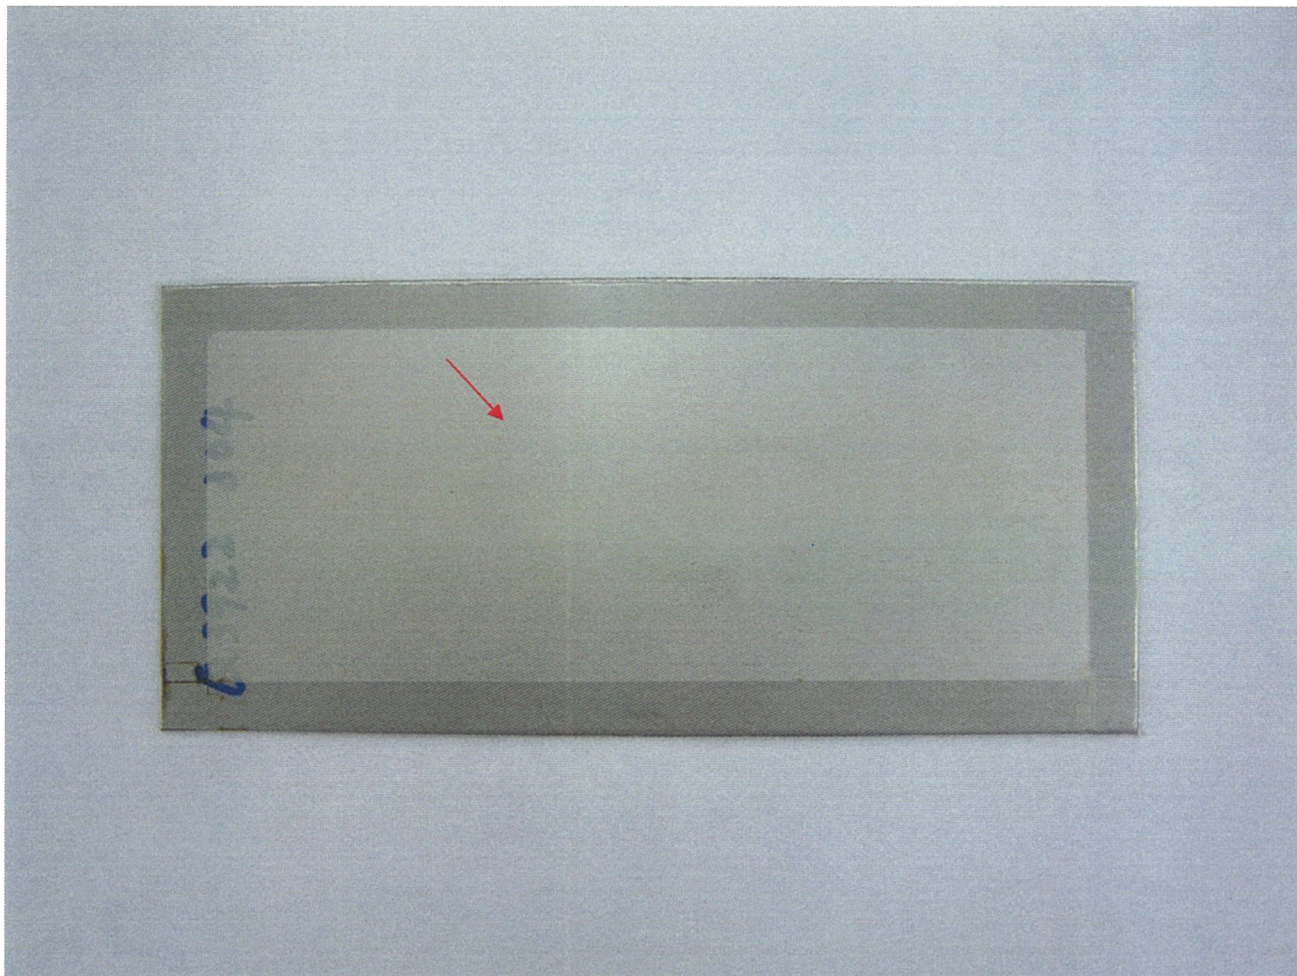
## 試驗報告



報告編號：KK-16-07147Z

頁數：5 OF 9

報告日期：106 年 01 月 25 日

=====  
試驗結果：

試件名稱：304 不銹鋼-1

試驗 2200 小時後

----- 5 -----

  
報告簽署人

本報告若有提供規範值，該規範值僅供參考，合格之判定以委託單位實際要求為準

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

TWC0576652



## 試驗報告

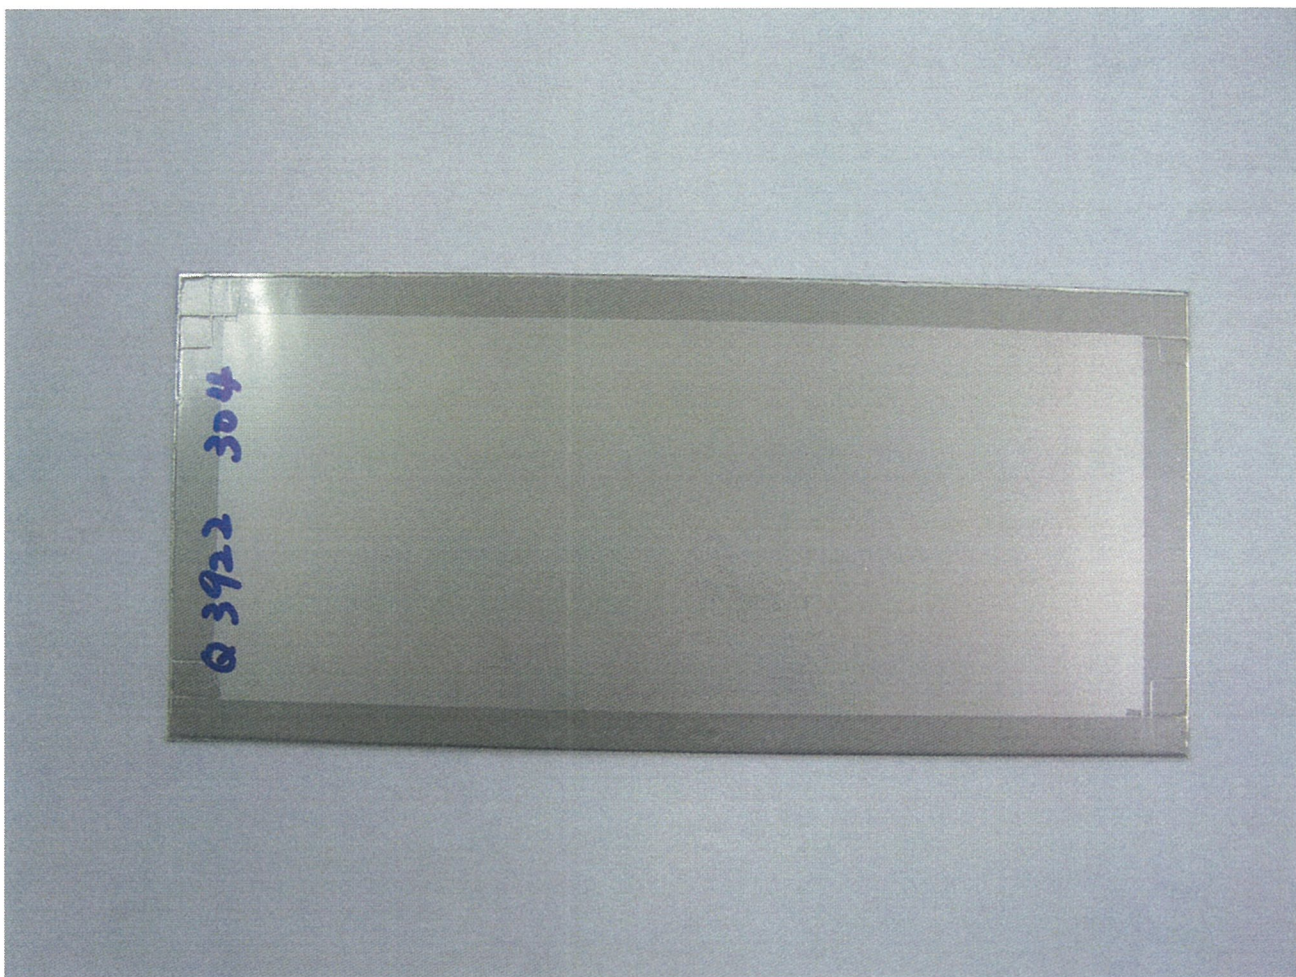


報告編號：KK-16-07147Z

頁數：6 OF 9

報告日期：106 年 01 月 25 日

試驗結果：



試件名稱：304 不銹鋼-2

試驗前

----- 6 -----

本報告若有提供規範值，該規範值僅供參考，合格之判定以委託單位實際要求為準

  
報告簽署人

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.

TWC0576653



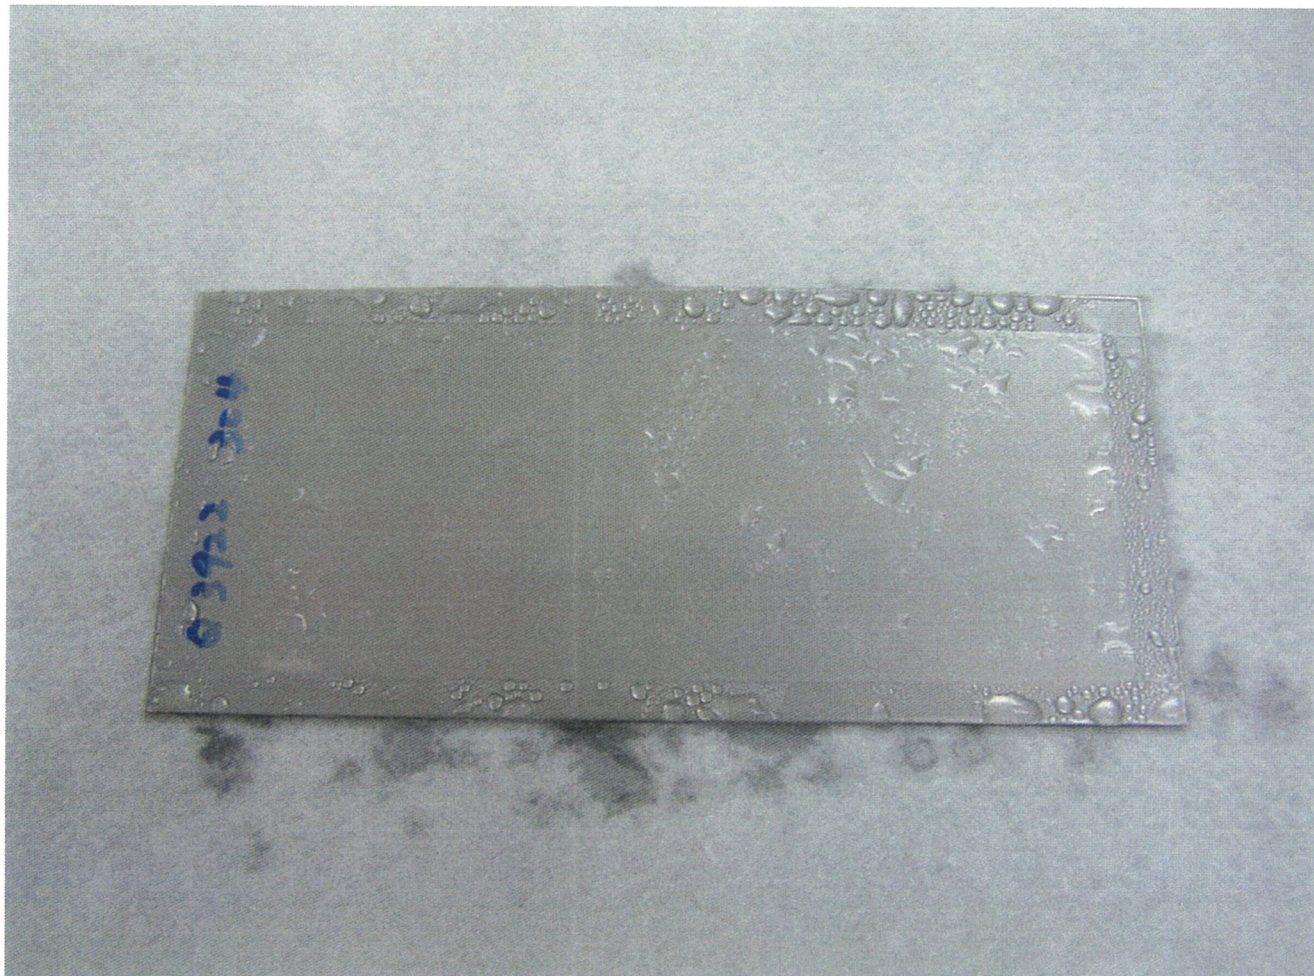
## 試驗報告



報告編號: KK-16-07147Z

頁數: 7 OF 9

報告日期: 106 年 01 月 25 日

=====  
試驗結果:

試件名稱: 304 不銹鋼-2

試驗 1920 小時後

----- 7 -----

  
報告簽署人

本報告若有提供規範值, 該規範值僅供參考, 合格之判定以委託單位實際要求為準

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.



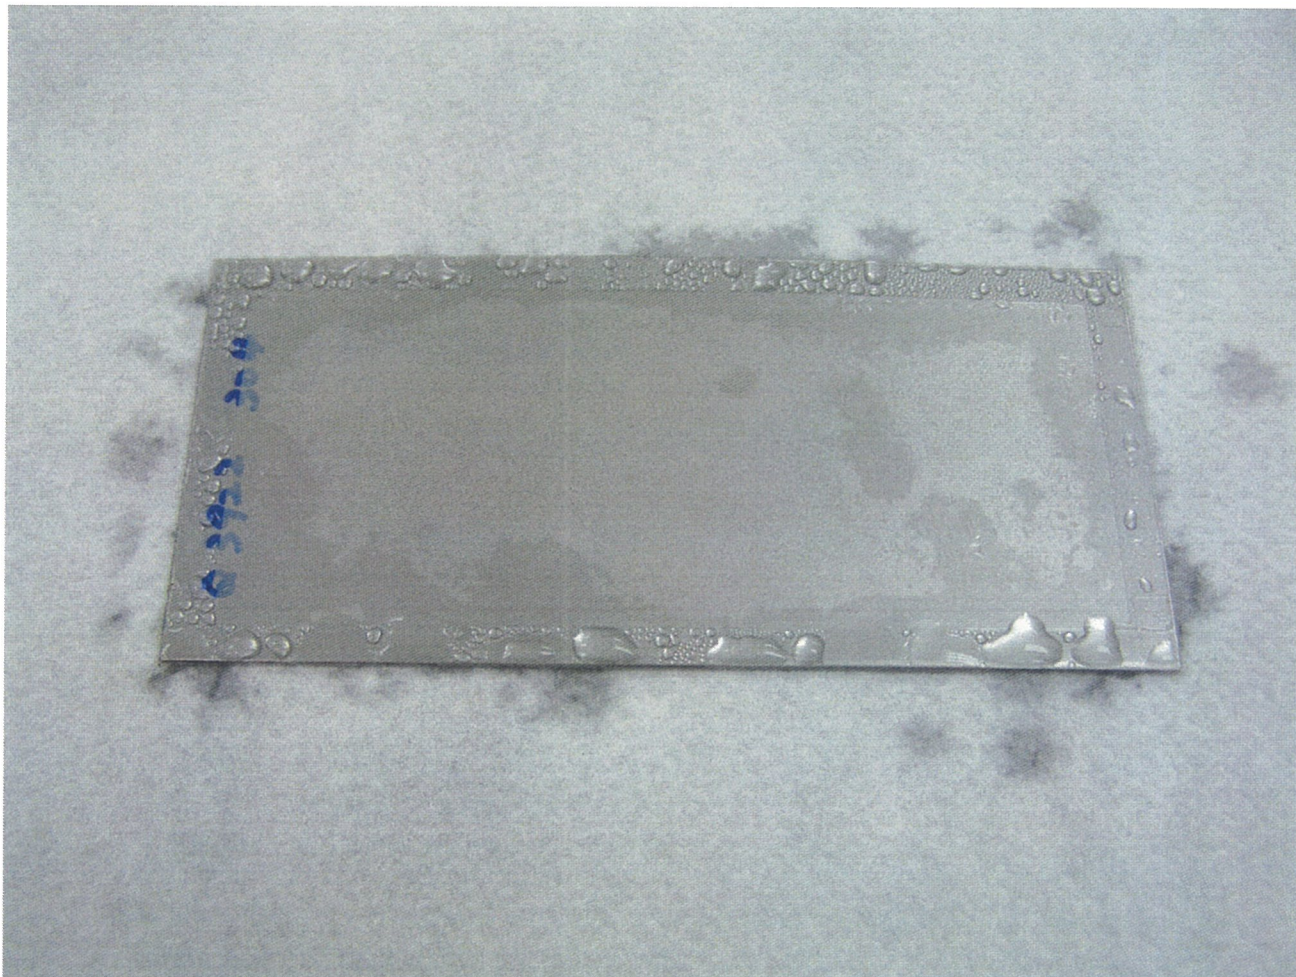
## 試驗報告



報告編號：KK-16-07147Z

頁數：8 OF 9

報告日期：106 年 01 月 25 日

=====  
試驗結果：

試件名稱：304 不銹鋼-2

試驗 2160 小時後

----- 8 -----

本報告若有提供規範值，該規範值僅供參考，合格之判定以委託單位實際要求為準

  
報告簽署人

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.



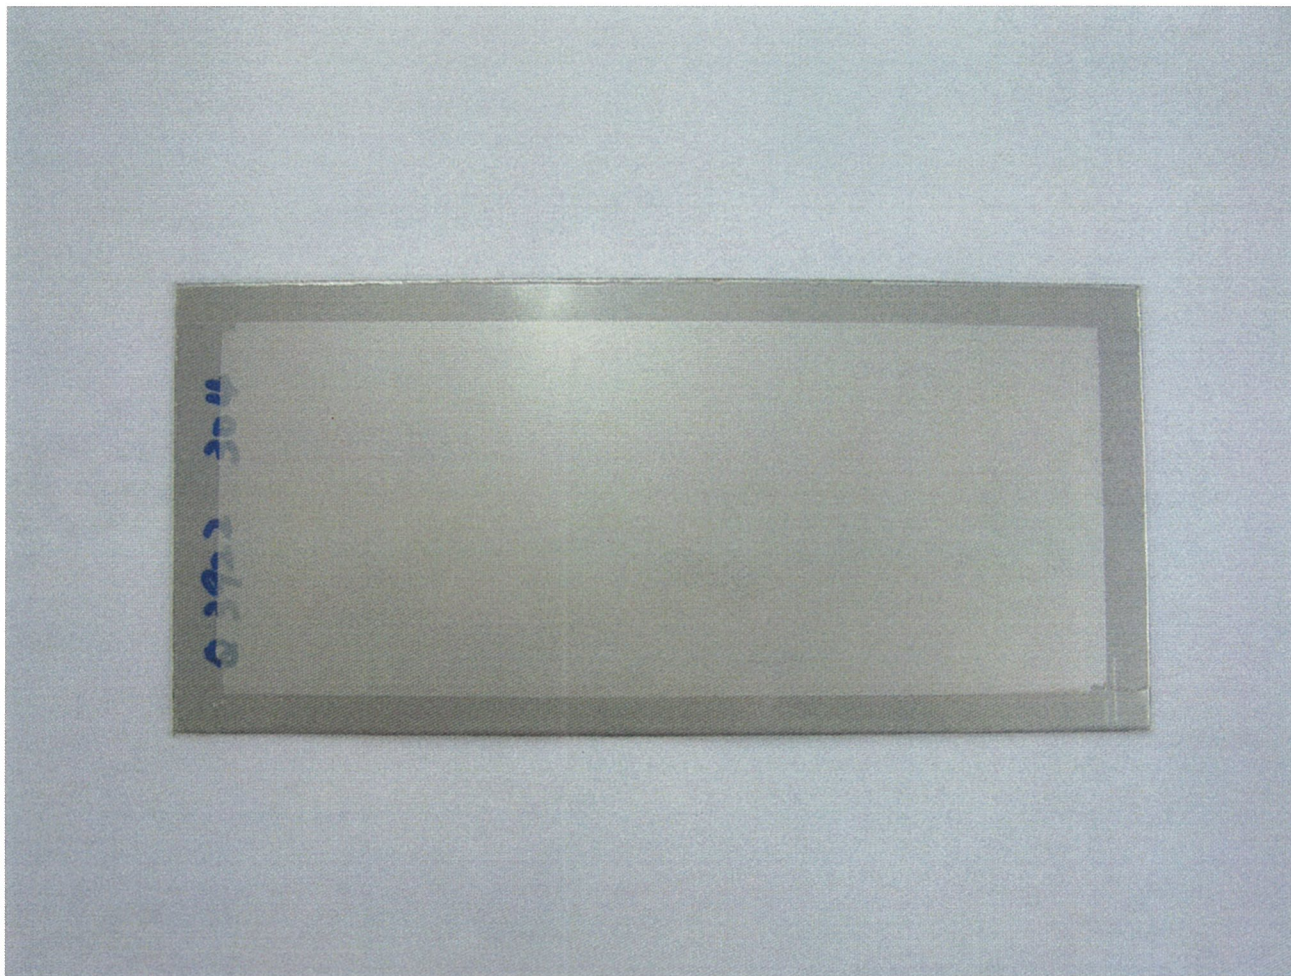
## 試驗報告



報告編號：KK-16-07147Z

頁數：9 OF 9

報告日期：106 年 01 月 25 日

=====  
試驗結果：

試件名稱：304 不銹鋼-2

試驗 2200 小時後

----- o O o -----

報告簽署人

本報告若有提供規範值，該規範值僅供參考，合格之判定以委託單位實際要求為準

This document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Document.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested.